

ab-plane resistivity and possible charge stripe ordering in strongly underdoped $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ single crystals

R.S. Gonnelli^a, V.A. Stepanov^b, A. Morello^a, G.A. Ummarino^a, D. Daghero^a, F. Licci^c and G. Ubertalli^d

^aINFM - Dipartimento di Fisica, Politecnico di Torino, c.so Duca degli Abruzzi 24, 10129 Torino, Italy

^bP.N. Lebedev Physical Institute, Russian Academy of Sciences, SU-117924 Moscow, Russia

^cIstituto MASPEC del CNR, Parco Area delle Scienze, 37/A - 43010 Loc. Fontanini - Parma, Italy

^dDipartimento di Scienza dei Materiali e Ing. Chimica, Politecnico di Torino, 10129 Torino, Italy

We have measured the *ab*-plane resistivity of $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ single crystals with small Sr content ($x=0.052\div0.075$) between 4.2 and 300 K by using the AC Van der Pauw technique. As recently suggested by Ichikawa *et al.*, the deviation from the linearity of the $\rho_{ab}(T)$ curve starting at a temperature T_{ch} can be interpreted as due to a progressive slowing down of the fluctuations of pre-formed charge stripes. An electronic transition of the stripes to a more ordered phase could instead be responsible for some very sharp anomalies present in the $\rho_{ab}(T)$ of superconducting samples just above T_c .

There is a growing experimental evidence [1,2] for the existence of charge stripes in $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ (LSCO) and the related compounds obtained by substitutions. Successive ordering transitions of these stripes, which seem to have a metallic character [3], possibly occur when the temperature is lowered. One would expect that, in superconducting samples, the phase transitions of the stripes occurring above T_c leave a mark on the electrical resistivity [3]. In the present work, we study the in-plane resistivity $\rho_{ab}(T)$ of strongly underdoped single crystals of LSCO, which exhibits, besides the usual features previously observed, an anomalous peak just above T_c . We relate it to an electronic transition of the stripes to a more ordered phase [4].

We carefully investigated the temperature dependence of the *ab*-plane resistivity of LSCO single crystals with small Sr doping ($0.052 \leq x \leq 0.075$). The crystals, having typical dimensions of about $1 \times 1 \times 0.3 \text{ mm}^3$, were grown by slowly cooling a non-stoichiometric melt. The chemical composition of every crystal was determined by means of EDS microprobe analysis and only crystals having a homogeneous Sr content were selected. In order to increase the precision of the *ab*-plane measure, we used

an AC version of the standard four-probes eight-measures Van der Pauw method injecting in the crystals AC currents of $100 \div 300 \mu\text{A}$ at 133 Hz. Details on the experimental technique are given elsewhere [5]. Fig. 1 shows the results. The crystals with $x = 0.052$ are not superconducting and show a low-temperature semiconducting-like behaviour of the resistivity, apart from an anomalous local maximum at about 25 K (curve *a* in Fig. 1). The crystals with $x = 0.06$ and 0.075 show well-defined superconducting transitions with midpoints at $T_c = 6.7 \text{ K}$ ($\Delta T_c = 0.6 \text{ K}$) and $T_c = 8.9 \text{ K}$ ($\Delta T_c = 2.2 \text{ K}$), respectively (curves *b* and *c*). However, very sharp anomalous peaks are present at temperatures about 2 K greater than T_c . The inset of Fig. 1 shows these peaks in greater detail. No anomalies are present in the AC susceptibility of the same crystals.

We first discuss the general behaviour of the resistivity curves. The $\rho_{ab}(T)$ at $150 < T < 300 \text{ K}$ is almost perfectly linear. We then fitted the resistivity in this region by using a linear model: $\rho_{ab}(T) = \alpha T + \beta$. Following a recent paper of Ichikawa *et al.* [3], we calculated the normalized resistivity $\rho_{ab}(T)/(\alpha T + \beta)$. The results for the superconducting samples are shown in Fig. 2. In Ref. 3 the deviations of the $\rho_{ab}(T)$ from the lin-

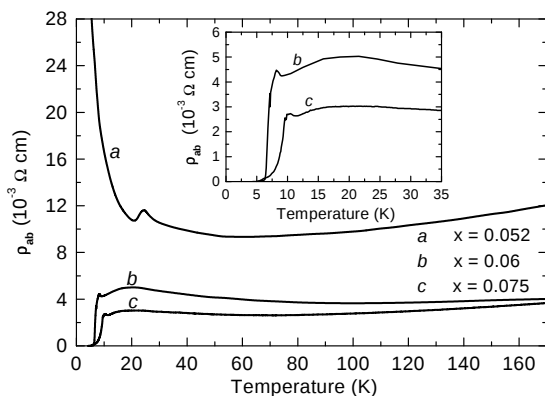


Figure 1. The ab -plane resistivity of our LSCO samples with $x = 0.052, 0.06$ and 0.075 (curves a, b and c , respectively). The inset shows an enlargement of the low-temperature part of curves b and c .

earity exceeding a certain threshold (dependent on x) have been associated to the localization of pre-formed stripes, which occurs at a temperature T_{ch} independently determined by Cu NQR measurements [2]. This correlation has been observed in Nd-substituted crystals but also in crystals without Nd, having $x=0.10$ and $x=0.12$ [3]. Following the same approach, we obtained the stripe localization temperatures T_{ch} in our samples by crossing the normalized resistivities with appropriate thresholds extrapolated from the data of Ref. 3. Solid circles on curves a and b of Fig. 2 show the results of this operation. The inset of Fig. 2 shows the temperatures T_{ch} of our crystals versus the Sr-doping (solid squares): they are in *excellent agreement* with T_{ch} values determined by means of NQR measurement in LSCO crystals with different doping [2] (open squares). A further decrease of the temperature below T_{ch} produces a continuous slowing-down of the stripe motion: stripes start to be pinned (by defects or by intrinsic low doping) and $\rho_{ab}(T)$ shows an up-turn up to a peak followed by the region dominated by superconducting fluctuations.

One could argue that the small peaks at T_o about 2 K above T_c (see the inset of Fig. 2) may be due to measurement errors, ρ_c interferences in ρ_{ab} , or crystal inhomogeneities (i.e. parts of the crystal are not superconducting and contribute to ρ_{ab} with a semiconducting-like term just above T_c). We can reply to these objections that (i) the Van der Pauw's four-probes AC technique provides four resistance measures and all of them

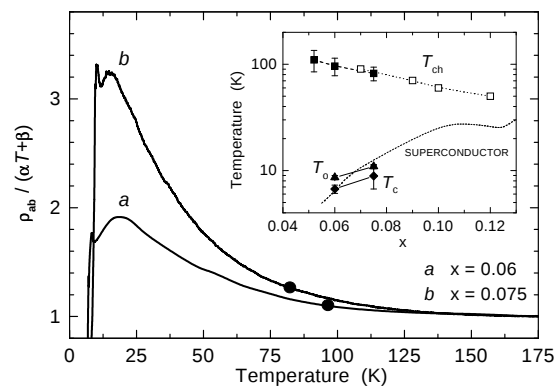


Figure 2. The normalized ab -plane resistivity of our samples with $x = 0.06$ (curve a) and 0.075 (curve b). The inset shows the temperatures T_{ch} , T_o and T_c determined from our resistivity data (solid symbols) and T_{ch} from NQR data [2] (open squares) as function of the doping (for details see the text).

show very reproducible peaks at T_o ; (ii) a detailed data analysis suggests that the resistivity contribution of c -axis terms or different-doping islands is unable to give peaks as those observed [5]. Another possible explanation for their origin could be a *structural* low-temperature transition, similar to that observed at higher temperature in Nd-substituted samples [3], but there are no other evidences of such a transition near T_c in LSCO.

We speculate that an *electronic* phase transition from a *nematic* stripe phase to a more ordered *smectic* one ("stripe glass") [4] is responsible for the anomalies near T_c . This scenario is supported by theoretical arguments [4] and experimental analogies with the behaviour of some metal dichalcogenides at the charge-density wave transition and it is consistent with the coexistence of cluster spin-glass and superconductivity recently observed below ~ 5 K in LSCO with $x = 0.06$ [6].

REFERENCES

1. J.M. Tranquada *et al.*, Phys. Rev. B 54 (1996) 7489.
2. A.W. Hunt *et al.*, Phys. Rev. Lett. 82 (1999) 4300; P.M. Singer *et al.*, cond-mat/9906140.
3. N. Ichikawa *et al.*, cond-mat/9910037; J.M. Tranquada *et al.*, Phys. Rev. B 59 (1999) 14712.
4. S.A. Kivelson and V.J. Emery, cond-mat/9809082; S.A. Kivelson *et al.*, Nature 393 (1998) 550.
5. R.S. Gonnelli *et al.*, to be published.
6. M.-H. Julien *et al.*, Phys. Rev. Lett. 83 (1999) 604.